

# Tuning the interaction between carbon nanotubes and dipole switches: Influence of the change of the nanotube-spiropyran distance

P Bluemmel<sup>1\*</sup>, A Setaro<sup>1</sup>, C Maity<sup>2</sup>, S Hecht<sup>2\*</sup>, and S Reich<sup>1</sup>

<sup>1</sup>DEPARTMENT OF PHYSICS, FREIE UNIVERSITÄT BERLIN, ARNIMALLEE 14, 14195 BERLIN

<sup>2</sup>DEPARTMENT OF CHEMISTRY, HUMBOLDT UNIVERSITÄT ZU BERLIN,  
BROOK-TAYLOR-STR. 2, 12489 BERLIN

*Email: bluemmel@physik.fu-berlin.de, sh@chemie.hu-berlin.de*

**Abstract.** The non-covalent functionalization of carbon nanotubes with spiropyran molecules, serving as optically addressable dipole switches, is reported. Two types of pyrene-spiropyran based dyads with spacers of different lengths resulting in different switch-tube distances were investigated. While both surfactants were able to form stable carbon nanotube suspensions, the different distances between the switch and the tube affect both of the components' optical properties. In the case of the shorter spacer, the nanotubes' luminescence as well as the merocyanine absorption band were red-shifted and furthermore, the rate of the merocyanine → spiropyran thermal back isomerization was decreased.

PACS numbers: 78.67.Ch, 42.79.Ta, 78.40.Ri, 77.80.Fm


## 1. Introduction

The functionalization of single walled carbon nanotubes (SWCNTs) with switchable molecules, as a way of tuning the electronic properties of SWCNTs recently became the subject of scientific investigation [1-3]. Molecular switches are chemical species possessing two or more (meta-) stable configurations [4]. Upon optical, chemical or other stimuli the molecules undergo structural changes leading to alternation of their electronic properties.

The spiropyran/merocyanine is a unique molecular switch couple that undergoes dramatic changes of its dipole moment (by more than 10 D) upon irradiation with light [5,6]. Following a non-covalent functionalization scheme, one could preserve the quantum nature of the tubes [7,8] (which is demolished by a covalent approach, which strongly increases the defectivity of the carbon network forming the nanotube [9,10]). Non-covalent functionalization is also expected to allow reversible tuning of the SWCNTs' properties, such as the band structure, affecting ballistic transport and exciton dynamics [11].

In the literature only few attempts of photochromic functionalization have been reported thus far [1-3,11,13]. However, these studies either focused on covalent functionalization methods - inducing defects in the nanotubes - or targeted pre deposited single nanotubes or nanotube films on substrates. Recently, we reported a method for producing stable suspensions of SWCNTs uniformly coated with a dipole switch made out of a spiropyran-based surfactant [14]. The SWCNTs' quantum nature could be maintained, as indicated by the bright infrared emission of the tubes, which had not been achieved before, neither through covalent nor non-covalent functionalization approaches. As bulk amounts of SWCNTs can be efficiently isolated and steadily suspended in solution, this method moreover opens up the chance of performing systematic studies on the interaction between the dipole switch and SWCNTs surface ruling out most other competing effects, such as intra-bundle tube-tube interaction or interaction with the substrate.

Here, we investigate the spacer length dependence of the interaction between the spiropyran switch and the SWCNTs. A pyrene anchor group was chosen to attach the switch compounds to the SWCNTs, as it has been proven to efficiently stick on the SWCNTs sidewall through  $\pi$ - $\pi$  stacking interaction [15]. To investigate the effect of varying the nanotube-switch distance, we synthesized two pyrene-spiropyran dyads with a short spacer (**S-PSP**: ~0.6 nm) and a long spacer (**L-PSP**: ~1.0 nm), connecting pyrene anchor and spiropyran/merocyanine switch moieties (Figure 1).

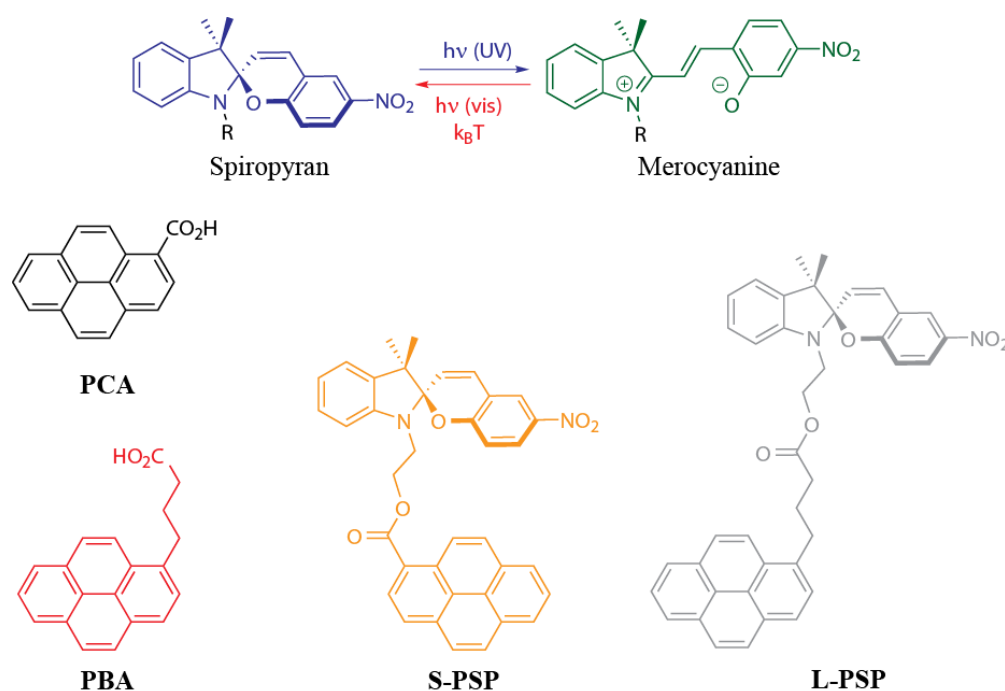


**Figure 1.** Photochromic equilibrium between the ring-closed spiropyran and its corresponding ring-opened merocyanine form as well as molecular structures of pyrene-1-carboxylic acid (PCA), pyrene-1-butanoic acid (PBA), and the pyrene-spiropyran dyads with short spacer (S-PSP) and longer spacer (L-PSP).

## 2. Synthesis and Switching Behavior of the Pyrene-Spiropyran Dyads

The desired pyrene-spiropyran dyads were synthesized via carbodiimide-mediated coupling of pyrene carboxylic acid derivatives i.e. pyrene-1-carboxylic acid and pyrene-1-butanoic acid with 1-(2-hydroxyethyl)-3,3-dimethyl-6'-nitroindolespirobenzopyran. The latter was synthesized from 2,3,3-trimethylindole via alkylation with 2-bromoethanol, followed by deprotonation with aqueous sodium hydroxide solution and final condensation with 5-nitro-2-hydroxybenzaldehyde (see supporting information).

Spiroyrans have two perpendicular  $\pi$  electron systems linked through a tetrahedral spiro carbon atom. Upon irradiation, the  $\text{C}_{\text{spiro}}-\text{O}$  bond of the closed form is broken and the formerly  $\text{sp}^3$ -hybridized spiro carbon atom adopts  $\text{sp}^2$ -hybridization and becomes planar to form the extended  $\pi$  conjugated system of the ring open merocyanine form, which is thus strongly colored. When the UV light source is removed, the molecules thermally revert to the initial colorless spiropyran isomer. In solution the ring closed spiropyran form exhibits an absorption maximum in the UV range between 320–380 nm. Irradiation of this absorption band causes ring opening and conversion to the merocyanine form which displays a broad and red-shifted absorption in the visible region of the spectrum between 450–650 nm. The absorption spectra of pyrene-spiropyran dyads are the mere superposition of the absorption spectra of the pyrene anchor and spiropyran switch components (see supporting information). From

the optical spectra it seems that there is negligible interaction between pyrene and spiropyran moiety in the ground state.

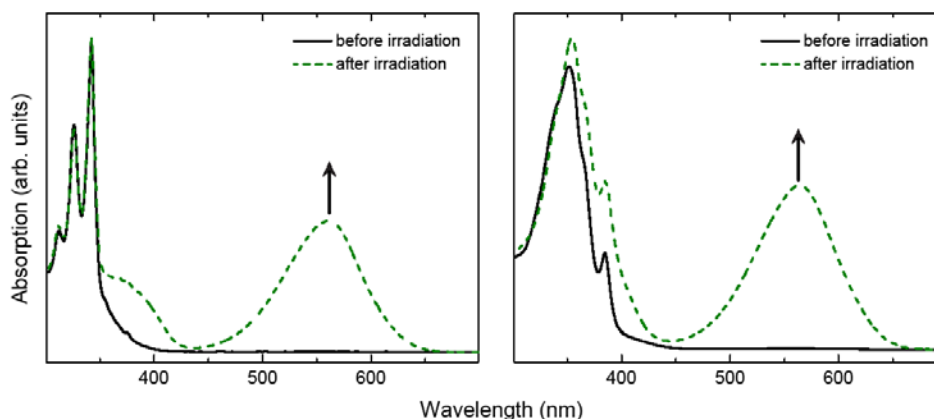

**Figure 2.** Absorption spectra of spiropyran dyads in THF ( $c = 1 \times 10^{-5}$  M): (left) UV/vis spectra of **L-PSP**, recorded before (black line) and after (green dashed line) irradiation with light of 350 nm wavelength. (right) UV/vis spectra of **S-PSP**, recorded before (black line) and after (green dashed line) irradiation with light of 350 nm wavelength. In both pictures the merocyanine absorption bands at 380 nm and 570 nm is observed after UV irradiation.


Irradiation of the pyrene-spiropyran dyads in tetrahydrofuran (THF) solution with light of 350 nm (3.5 eV) wavelength leads to the formation of new absorption bands at around 570 nm (2.2 eV) as well as at 380 nm (3.3 eV), both characteristic of the ring-opened merocyanine form (Figure 2). The absorption band of the pyrene moiety with its typical vibronic fine-structure remains unchanged. UV irradiation led to the opening of the spiropyran moiety to its corresponding merocyanine form. The spectral perturbation resulting from UV irradiation of the dyads decays with time after irradiation ceases and the original spectrum is recovered. The decay is exponential and is ascribed to thermal closing of the merocyanine to regenerate the spiro form, i.e. so called T-type photochromism [4]. Hence in THF and at room temperature the spiropyran is the most stable form of the molecule. The transformations between ring-closed spiropyran isomer and ring-opened merocyanine isomer are reversible.

### 3. Characterization of SWCNTs Functionalized with Pyrene-Spiropyran Dyads

Investigation of the UV/vis absorption spectra of **PCA**, **PBA**, **S-PSP** and **L-PSP** in THF solution shows that the pyrene anchor group's characteristic absorption bands seen in **PCA** and **PBA** are not significantly altered in the presence of the spiropyran switching moiety, i.e. **S-PSP** and **L-PSP**, respectively (Figure 3, left).


When SWCNT suspension stabilized by either **PCA**, **PBA**, **S-PSP**, or **L-PSP** were measured, the typical  $M_{11}$  and  $S_{22}$  absorption bands of carbon nanotubes in the visible spectral region could clearly be discerned (Figure 3, right). All four different suspensions exhibit similar spectral contributions

from the different absorption bands indicating similar sample compositions. Note that the merocyanine's characteristic absorption maximum at 570 nm is absent in the **S-PSP** and **L-PSP** spectra (orange and gray line in Figure 3, right) and hence the switches have not undergone a ring-opening reaction upon complexation to the SWCNTs.

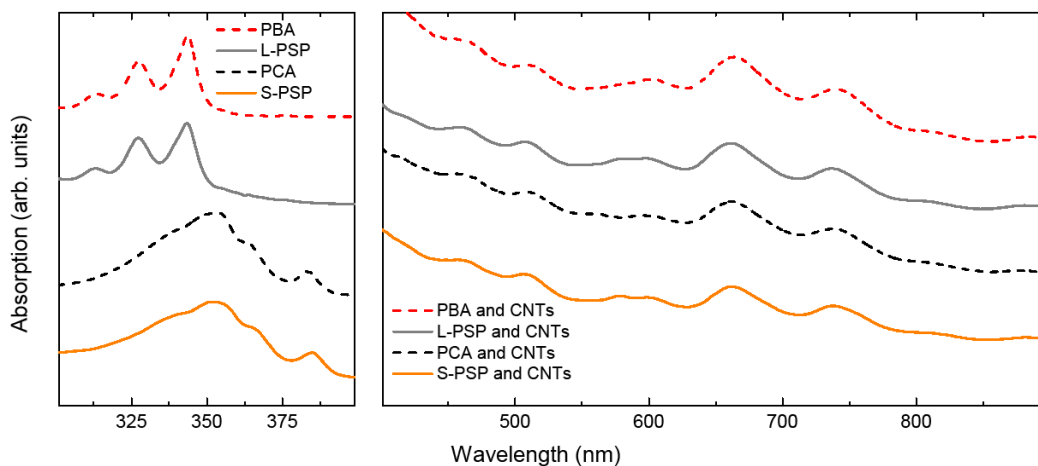

**Figure 3.** Absorption spectra of **PCA**, **PCA**, **S-PSP**, and **L-PSP** (left) as well as their suspensions with SWCNTs (right) in THF at 25 °C: The spectra on the left show the characteristic pyrene absorption in the UV region is clearly visible and not altered by the presence of the switch (left). The visible region shows the M11 and S22 absorption bands of the SWCNTs stabilized as a suspension by the pyrene-spiropyran dyads (right).


By obtaining the photoluminescence excitation (PLE) maps of the **S-PSP**- and **L-PSP**-stabilized SWCNT suspension, it is possible to conveniently determine the approximate chirality distribution of the semiconducting carbon nanotubes within the sample based on the relative luminescence intensities [8]. For SWCNT samples using either of the two molecules, a very similar distribution of nanotubes has been observed (Figure 4). In both samples the most abundant species are the (8,4) and (7,6) tubes, while all other chiralities show more or less similar contributions. This nicely illustrates the fact that the binding interaction between the molecules and nanotubes remains very similar, exhibiting more or less the same composition in the isolation and solubilization process based on the use of pyrene as an anchor group. This was expected as changes in the anchoring moiety have been shown to affect the sample composition [16,17].

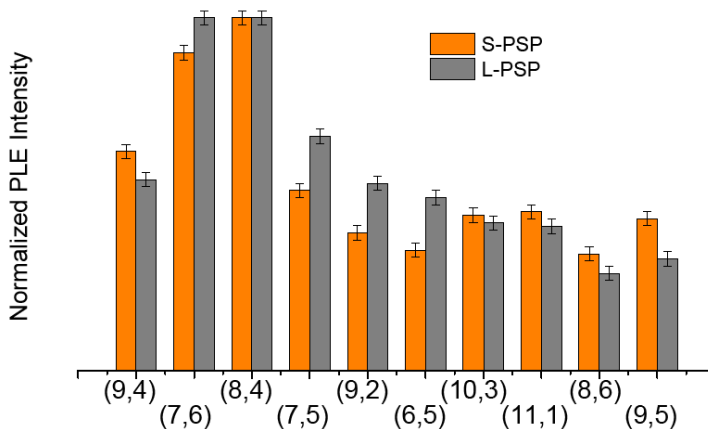

**Figure 4.** Contributions of SWCNTs of different chirality in suspensions using either S-PSP or L-PSP as surfactants as revealed from obtained photoluminescence excitation (PLE) maps.

Although the spacer length does not affect the intensity distribution of the various nanotubes, a shift in the positions of the peaks within the PLE charts was observed between the two samples. The luminescence energies of both the (7,5) and (7,6) tubes, functionalized with either **S-PSP** or **L-PSP**, differ by 3 meV (Figure 5). This is expected, as the charge carriers in the nanotubes couple to the dipole moment of spiropyran, and alter the electronic properties of the tubes [11]. As the distance becomes smaller, the coupling strength increases and the effect becomes more pronounced.


Malic *et al.* calculated the dipole moment of spiropyran to 6.2D, while the dipole moment of merocyanine is 13.9D, similar to what has been observed experimentally [11,12]. It is important to note that the direction of the dipole moment changes upon isomerization. The dipole moments of spiropyran and merocyanine are approximately orthogonal and, thus, the component of the spiropyrans dipole moment in the merocyanine direction is almost zero.”

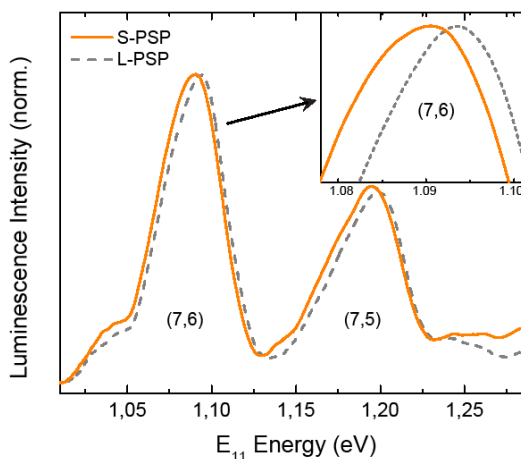

**Figure 5.** Normalized luminescence spectra of SWCNT samples coated either with **S-PSP** or **L-PSP** in THF upon excitation at 650 nm (1.907 eV): In the case of the longer spacer (**L-PSP**) a slight but reproducible red-shift of 3 meV as compared to **S-PSP** is observed (see inset).

Up to now, we investigated only the interaction of the spiropyran dyad with the nanotubes. Upon switching the spiropyran converts to the merocyanine form, which is a planar molecule with an extended  $\pi$ -system that should interact more strongly with the tubes. The interaction between the tubes and the attached switches is expected to alter upon irradiation and, importantly, the intensity of such interaction should in principle be dependent on their relative distance, i.e. the spacer length [11].

After UV induced switching to the ring-opened merocyanine form, two effects were observed in the absorption spectra: First, the position of the merocyanine absorption band around 570 nm changes depending on the spacer length (Figure 6). Considering the parent spiropyran as a pyrene-spiropyran dyad with infinite spacer length and comparing the position of the merocyanine band with the dyads of long and short spacer length, a systematic red shift of the absorption band with decreasing spacer length was observed, which is most likely due to the increasing interaction between the merocyanine's and the pyrene's  $\pi$ -systems. Note that, as all samples were prepared in THF, solvent effects can be ruled out as a source of this red shift. Second, complexation to the carbon nanotubes seems to reverse the pyrene-induced red shift to a certain extent. The peaks shift back towards their original positions in the blue after nanotube functionalization. This opposing effect is most likely due to the dominating pyrene-SWCNT  $\pi$ - $\pi$  interaction, leading to a lower disturbance of the merocyanine  $\pi$ -system.

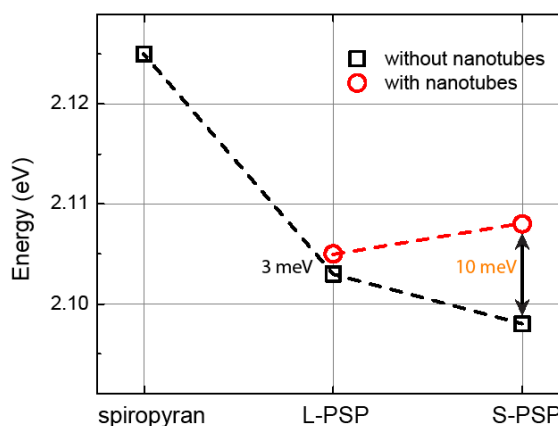

**Figure 6.** Positions of the merocyanine absorption band upon UV irradiation with 366nm for the parent spiropyran (without SWCNTs) and for the pyrene-spiropyran dyads (**L-PSP** and **S-PSP** in the presence and absence of SWCNTs). Note that all samples were prepared in THF.

Perhaps most interestingly, the tube-dipole distance not only affects the electronic properties of switch molecule by tuning the spectral position of the merocyanine absorption band, but furthermore influences the kinetic behavior of the isomerization processes (Table 1). The switching behavior of the spiropyran moiety is very similar for both compounds, i.e. **S-PSP** and **L-PSP**, in neat solution, while it

changes drastically in the presence of the nanotubes. For the dyad molecule with the long spacer, the tube-switch distance seems to be large enough to confer only little change to the dynamics, whereas for the dyad molecule with the short spacer, the time necessary to achieve the thermal ring closing isomerization is increased by 25%. This can be attributed to the stabilizing effect of the SWCNTs outer surface on the merocyanine form due to enhanced  $\pi$ - $\pi$  interactions, if the spacer is short enough. On the contrary, the effect on the photochemical forward reaction, converting the spiropyran to the merocyanine, is negligible within experimental error. However, as carbon nanotubes give rise to scattering and inner filter effects, this is not self-evident and further investigation of the quantum yields are necessary to gain more insight into the fundamental processes taking place.

**Table 1.** Switching dynamics of the spiropyran-merocyanine switching system both in the presence and absence of SWCNTs. Shown are the times for the photochemical ring-opening reaction ( $t_{\text{spiro} \rightarrow \text{mero}}$ ) and the thermal ring-closing isomerization ( $t_{\text{mero} \rightarrow \text{spiro}}$ ).

	S-PSP		L-PSP	
	without SWCNTs	with SWCNTs	without SWCNTs	with SWCNTs
$t_{\text{spiro} \rightarrow \text{mero}}$ [s]	31±2	32±2	35±6	29±1
$t_{\text{mero} \rightarrow \text{spiro}}$ [s]	39±2	48±2	32±5	36±2



#### 4. Conclusion

The functionalization of SWCNTs with two pyrene-spiropyran dyads with different spacer lengths has been accomplished and the influence of variation of the tube-spiropyran separation has been investigated. As both molecules utilize pyrene as a non-covalent anchor to adsorb onto the surface of carbon nanotubes, the relative composition of the nanotube chirality distribution inside the samples is similar using both surfactants.

Although the distribution of the peak intensities of the nanotubes in the suspensions are affected only by the morphology of the anchor, the different distances between anchor and dipole switch alter the position of the peaks themselves: a slight red shift (ca. 3 meV) between the emissions of nanotubes coated with **S-PSP** and **L-PSP** was observed.

In addition the spiropyran itself is affected by the distance to the nanotubes. The red shifted merocyanine absorption band at 570 nm implies a stronger  $\pi$ - $\pi$  interaction of the merocyanine isomer and the nanotubes sidewall when decreasing the spacer length of the dyad. Furthermore, we found that at shorter distances carbon nanotubes are able to stabilize the merocyanine form of the switch molecules, which slows down the merocyanine  $\rightarrow$  spiropyran thermal back isomerization.

#### Acknowledgements

Generous support by the German Research Foundation (DFG via SFB 658, subprojects A6 and B8) as well as the ERC (grant number 210642) is gratefully acknowledged. Wacker Chemie AG, BASF AG, Bayer Industry Services, and Sasol Germany are thanked for generous donations of chemicals.

#### References

- [1] Guo X F, Huang L M, O'Brien S, Kim P, and Nuckolls C 2005 *J. Am. Chem. Soc.* **127**(43) 15045–15047
- [2] Zhou X, Zifer T, Wong B M, Krafcik K L, Léonard F and Vance AL 2009 *Nano letters* **9**(3): 1028-33
- [3] Simmons J, In I, Campbell V, Mark T, Léonard F, Gopalan P, and Eriksson M 2007 *Physical Review Letters* **98**(8) 1-4
- [4] Feringa B 2001 *Molecular Switches* ed Feringa B (Wiley-VCH) p 476

- [5] Russew M-M, and Hecht S *Advanced Materials* **22**(31) 3348-60
- [6] Guo X, Zhang D, Wang T, and Zhu D 2003 *Chemical Communications* **7** 914-5
- [7] Reich S, Thomsen C, and Ordejón, P 2002 *Physical Review B* **65**(15) 1-11
- [8] Bachilo S M, Strano M S, Kittrell C, Hauge R H, Smalley R E, and Weisman R B 2002 *Science* **298**(5602) 2361-6
- [9] Hirsch A, and Vostrowsky O 2005 *Top Curr Chem* **245** 193- 237
- [10] Balasubramanian K, and Burghard M 2005 *Small* **1**(2) 180-92
- [11] Malic E, Weber C, Richter M, Atalla V, Klamroth T, Saalfrank P, Reich S, and Knorr A 2011 *Physical Review Letters* **106**(9) 1-4
- [12] Atassi Y, Chauvin J, Delaire J A, Delouis J-F, Fanton-Maltey I, and Nakatani K 1998 *Pure and Applied Chemistry*, **70**(11) 2157-2166
- [13] Del Canto E, Flavin K, Natali M, Perova T, and Giordani S 2010 *Carbon* **48**(10) 2815-2824
- [14] Setaro A, Bluemmel P, Maity C, Hecht S and Reich S 2011 *Adv Funct Mat*, **submitted**
- [15] Chen R J, Zhang Y, Wang D and Dai H 2001 *Journal of the American Chemical Society* **123**(16) 3838-3839
- [16] Setaro A., Popeney C S, Trappmann B, Datsyuk, V, Haag R, and Reich S 2010 *Chemical Physics Letters* **493**(1-3) 147-150
- [17] Marquis R, Greco C, Sadokierska I, Lebedkin S, Kappes M M, Michel T, Alvarez L, Sauvajol J-L, Meunier S, and Mioskowski C 2008 *Nano Letters* **8**(7) 1830-5